

Green gold production from primary and secondary resources

Alexander Birich, Bernd Friedrich*

RWTH Aachen University, Institute for Process Metallurgy and Metal Recycling

ARTICLE INFORMATION :

<https://doi.org/10.30544/MMD7>

Received: 24 June 2023

Accepted: 30 June 2023

Type of paper: Review paper



Copyright: © 2023 by the authors, under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons-mons.org/licenses/by/4.0/>).

ABSTRACT

The excellent chemical resistance of gold is an important property of the precious metal, but it becomes a disadvantage when it comes to gold extraction. Many metallurgical processes are based on highly aggressive or toxic reagents. Especially artisanal and small-scale gold mining activities are heavily criticized, as their environmental impact can hardly be controlled. Ecological concerns are forcing society and industry to find a solution for efficient gold recovery by the use of alternative methods to replace the mercury or cyanide process. In the last decades, many alternative leaching reagents have been investigated extensively. Researchers showed promising results in terms of technical and environmental characteristics. Furthermore, different demonstration and pilot-scale application tests were conducted around the world to generate information for a potential industrial application. Nevertheless, to this day there is just one reported industrial-scale application using the cyanide alternative thiosulfate. Besides chlorination or aqua regia in refineries and the recycling of specific waste streams, there is no notable industrial application of cyanide alternatives. Especially gold recycling from secondary resources would have a high ecological impact, as mining activities would be reduced. For example, electronic waste is a resource growing in volume and importance for gold recovery but lacking an efficient decentralized process.

In this work, the potential of cyanide alternative reagents for industrial application in gold production and recycling is discussed, along with various reasons that explain the restrained acceptance of gold producers.

Keywords: Gold, Cyanide Alternatives, Green Gold, Recycling.

1. Introduction

Since its inception in the late 1800s, cyanidation has been the dominant process for the recovery of gold and silver from ores, due to its simplicity and cost efficiency. The main disadvantage of cyanide is related to environmental issues, which may occur due to improper storage and transport or failed tailings management and storage. Industrial gold producers barely face critical, or deadly accidents, but these problems especially occur for unregulated, small-scale operations in the informal sector. The informal sector, which includes small-scale miners, accounts for approximately 20 % of the world's primary gold production. Especially the application of mercury for gold recovery has detrimental effects on the environment and human health, including contaminated water sources, soil degradation, and toxic exposure

(Marsden 2006; Springer et al. 2020). With rising ecological awareness, public pressure on gold extraction is rising continuously. There are many alternative reagents to cyanide that have been intensively investigated and tested up to pilot scale in the last decades, including thiosulfate, thiourea, and halides. Despite their general capability for gold extraction and much lower environmental hazards, alternative reagents have barely been adopted in the gold mining industry (Aylmore 2016). At the same time, consumers' demand for "green gold" rises, and progressively more companies are abandoning gold from primary production (e.g., smartphone producers and jewelry).

Recycling helps to supplement the global gold supply by providing a significant source of secondary gold. According to the World Gold Council, approximately one-third of the world's annual gold supply comes from recycled gold. The main resources for gold recycling arise from such as jewelry, coins, electronic waste (e-waste), and industrial by-products (Fritz et al. 2020).

* Corresponding author.
E-mail address: abirich@ime-aachen.de (Bernd Friedrich).

2. State of the Art Gold Production

2.1. Cyanidation

Since its inception in the late 1800s replacing the early chlorination process (Plattner process), cyanidation has been the primary process for the extraction of gold and silver from ores due to its technical and economic merits (Hilson und Monhemius 2006; Marsden 2006):

Highly efficient and stable process (simple and well-established chemistry);

Alkaline, non-corrosive process (low-cost construction material);

Low reagent consumption for most ore types;

Established, effective downstream gold recovery process;

Availability of efficient industrial processes for detoxification of effluents.

The main detractor to cyanide leaching is environmental issues associated with the use, storage, and transport of cyanide due to its high toxicity to humans and many living organisms even at very low concentrations (Göknelma et al. 2016). With increasing public pressure and increasingly tightening regulations, the gold industry could even face a widespread ban on the use of cyanide. Consequently, an increasing number of feasible gold mine projects could not be realized, or their development was stopped in an early stage due to social opposition. Besides environmental concerns, cyanide shows some technical limitations. The industrial gold recovery becomes more difficult, easy-to-process deposits are depleted and gold producers are forced to use complex, refractory, and carbonaceous preg-robbing ores (Marsden 2006).

2.2. Informal Gold Sector

The informal sector accounts for approximately 20 % of the global primary gold production, mainly from deposits that are located in remote areas or forests and therefore cannot be exploited by large industries. Gold is recovered via underground mining, processing of secondary deposits with sluice boxes or from riverbeds (Springer et al. 2020; Kahhat et al. 2019). While this sector can provide a source of income for many individuals and small communities, it is often associated with illegal practices, including the use of harmful chemicals like mercury or cyanide. These practices can have detrimental effects on the environment and human health, including contaminated water sources, soil degradation, and toxic exposure. Many efforts were made to improve transparency, formalize the sector, and promote sustainable mining practices, without success. It is frequently neglected that the informal sector wants to maintain its independence, which could be at risk if other mining techniques are used. Legal regulations are not effective, as the informal mining takes place in very abundant areas (Springer et al. 2020; Wotruba et al. 1998).

The environmental damage of amalgamation is particularly devastating in Indonesia. Although the Indonesian government banned mercury in small-scale gold mining in 2018, its application could not be curbed, since informal mercury production was established supplying the miners. The black-market was that prosperous, that Indonesia became a major global supplier of mercury in 2016 (report final 2022). A major problem is the lacking awareness of miners and local communities for the health and environmental hazards of mercury. Throughout the country, gold miners work with mercury without fear to be punished. The police are even accused of actively contributing to the distribution of the mercury process, while also governmental employees participate on the revenue. It is estimated that this mining practice have poisoned approximately 500 000 people in the last decades (Paddock 2019; Satriastanti 2015). A similar situation prevails in Brazilian Amazonas. Just approximately 10 % of artisanal miners work legally, because claiming mining rights is very bureaucratic and expensive. Gold mining is organized by individuals who own the required equipment, open

camp, and hire miners, who are paid with a share of the recovered gold. In the absence of the government, these structures have strengthened, and miners understand their activities to be illegal since they are not prosecuted (Springer et al. 2020; Kolen et al. 2018, 2013).

2.3. Gold Recycling

Gold recycling is an essential component of the global gold supply chain, due to the depletion of easy-to-access gold deposits. Recycling gold not only helps to meet this demand but also helps to reduce the environmental impact of gold mining, as it requires much less energy and shows significant economic benefits. Comparing the global warming potential of gold recovery processes, one can see the importance of recycling: 16 t CO₂-Eq. for mining, 1 t CO₂-Eq. for electronic waste recycling, and just 53 kg CO₂-Eq. for high-value gold scrap (Fritz et al. 2020). According to the World Gold Council, the total global recycled gold accounted for approximately 1144 t in 2021, which is around 24 % of the global supply. The main applications of gold are jewelry, which has an average life span of 50 years, and the investment sector, which are barely available for recycling (Fernandez und Klimas 2019). Gold from electronics, medical or other applications is often not recycled due to insufficient collection (Birich 2020). These circumstances explain why the global gold demand cannot be satisfied just by gold recycling. In 2018, 23 % of the gold supply was recycled from high-grade waste such as jewelry and coins followed by e-waste with 3 % (Fritz et al. 2020). Nevertheless, E-waste is considered an important resource, because of its wide application and fast-growing production.

Chlorination and aqua regia are industrially used worldwide for refining of gold but also for the recycling, for jewelry, coins, medical or industrial residues, while e-waste is mainly recycled in the pyrometallurgical copper route. Although there are many studies on gold recovery from e-waste by using cyanide alternative reagents, there is no commercialized, environmentally sound process (Birich 2020; Latacz et al. 2020). Nevertheless, there are many informal businesses around the world that use aqua regia to recover gold under harsh environmental and safety conditions. In China, for example, e-waste is mostly recycled in the informal sector, where a huge number of trash recyclers are engaged to use crude and polluting recycling technologies to quickly separate gold and other precious metals (Chi et al. 2011). Similar, India is facing an expanding dilemma with the growth of the informal recycling sector, which releases hazardous organic pollutants, aggressive effluents and other toxicants (Chakraborty et al. 2018)

Own research proved the applicability and advantages of cyanide alternative leaching reagents, as displayed in [Figure 1](#). Especially Cu is a critical contaminant in e-waste for gold leaching, as it is dissolved by most reagents causing a chemical consumption and other negative side effects. Nonetheless, especially thiourea and thiosulfate were capable to achieve a good gold recovery. Just when the initial Cu concentration of the input material is strongly reduced, also cyanide achieves a reasonable gold recovery but anyway being less selective to copper (Birich et al. 2023).

The leaching experiments were validated on different waste streams from electronic equipment reaching robust gold recovery of more than 95 %, for PCB reproducibly more than 98 % ([Figure 2](#)). A nearly complete gold recovery can be achieved in less than 4 hours, which is also a benefit of cyanide alternative reagents (Birich et al. 2018; Birich et al. 2019; Birich et al. 2023).

3. Industrial Application of Cyanide Alternative Reagents in Primary Gold Production

Environmental issues appear to be the major stimulus for the search and development of alternative leaching systems for gold and silver extraction. To overcome the drawbacks of cyanide, many alternative reagents were intensively investigated for their capability as a suitable

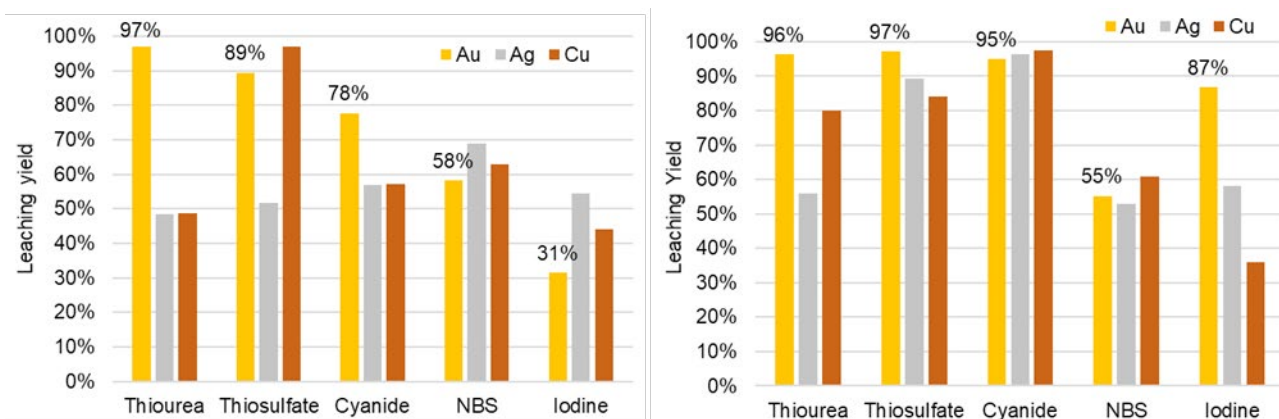


Fig. 1. Leaching of pyrolyzed and crushed RAM PCB after foregoing base metal leaching (left: initial Cu-concentration 16.8 wt.%; right: initial Cu-concentration 1,3 wt.%) (Birich et al. 2023)

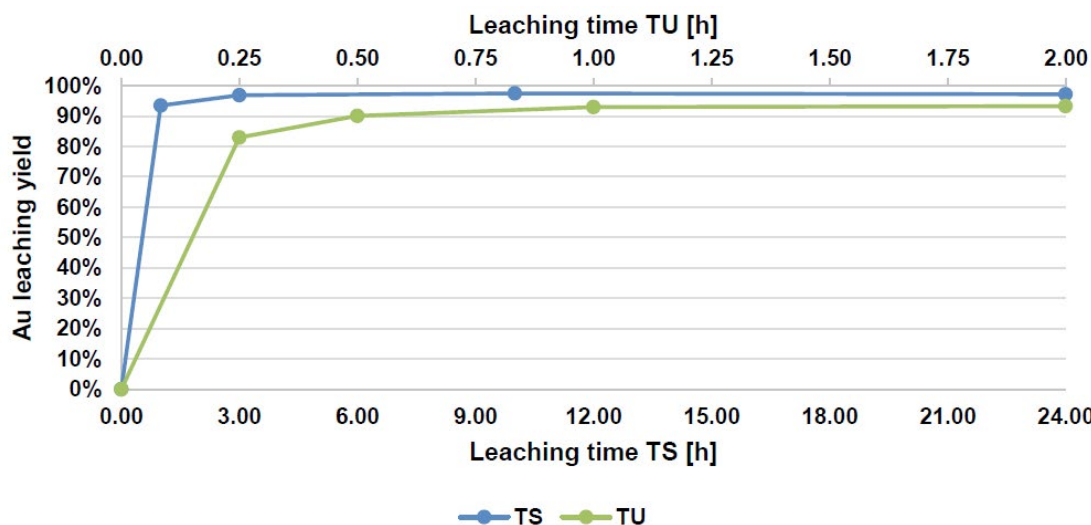


Fig. 2. Gold dissolution from pyrolyzed and pre-leached and comminuted RAM PCBs via thiourea TU and thiosulfate TS over time (Birich et al. 2023)

gold extractant (Aylmore 2016) reported 27 lixivants that have been researched as alternatives to cyanide for leaching gold, which were successfully tested at lab scale and partially transferred to pilot scale tests. However, despite potential advantages, many of those lixivants tested are essentially of academic interest with very limited prospects for commercial exploitation.

This chapter summarizes relevant activities for industrial implementation of cyanide alternatives. Many lixivants have not been tested in larger scale than laboratory due to environmental, technical, or economic constraints. The leaching mechanism and other details are not discussed in this study, as they are well described in literature.

3.1. Thiosulfate

Thiosulfate has received particular attention as an alternative to cyanide in recent years, although its use dates to the mid-19th century. Thiosulfate leaching was first used in the “Von Patera Process” in 1858. In this process, silver was extracted using sodium thiosulfate solutions after chlorination roasting of the ore (Molleman und Dreisinger 2002). Newmont Gold Co. operated a pilot plant for the extraction of gold using ammonium thiosulfate solutions from a refractory ore (preg-robbing) by heap/column leaching in 1996 - 1999. In the pilot plant, gold cementation with Cu/Zn powders was applied (Wan und LeVier 2003). In 1998, Placer Dome Co. applied gold extraction from preg-robbing type refractory ores using a Cu(II)-ammonia-thiosulfate system in pilot scale (West-Sells und Hackl 2005). The process had two different applications: Mill Ammonium Thiosulfate for tank leaching and Heap Ammonium Thiosulfate. Ammonium sulfide ((NH₄)₂S) was

used for gold recovery from PLS. Neither the Newmont nor the Placer Dome processes were commercialized. More recently, a demonstration plant for the application of a thiosulfate leaching process for small gold deposits has been built in Australia. The operation seems to involve vat leaching of gravity tails followed by gold recovery from PLS by ion exchange (Breuer 2017; Heselev 2017). After 20 years of R&D studies, Barrick Gold Co. developed a technically and economically viable thiosulfate leaching process. In 2015, a commercial thiosulfate leaching facility at the Goldstrike mine (Nevada/USA) started processing a double refractory ore (see Figure 3). Cyanide gold recovery of this ore type was just 30 % (Aylmore 2016; Choi 2016). The process is a non-ammoniacal process that uses Cu(II) and calcium thiosulfate (CaS₂O₃) and operates at pH 8. Before leaching, pressure oxidation (225°C, 7 bar p_{O₂}, 1 h) and neutralization to pH 8 - 8.5 is applied. Gold is recovered from PLS by a resin-in-leach (RIL) process. Thiosulfate regeneration is accomplished in contact with sulfites and elemental sulfur derived from partial oxidation of sulfide ores during pressure leaching at 150 °C (Evans et al. 2017; Choi und Chefai; Choi et al. 2013).

Despite several environmental and technical advantages of thiosulfate, there are some technical and economic constraints, especially in the solution purification and gold recovery stage (Xia 2008; Zhang und Dreisinger 2004). In addition, reagent consumption may be high under certain conditions, owing to the need for higher thiosulfate addition. Therefore, the reagent concentration is often significantly higher than in cyanide leaching i.e., 11-22 g/L thiosulfate vs. 0.25 - 1 g/L cyanide (Xie et al. 2021; Marsden 2006). These are the main reasons for the unique application of the thiosulfate process by Barrick Gold.

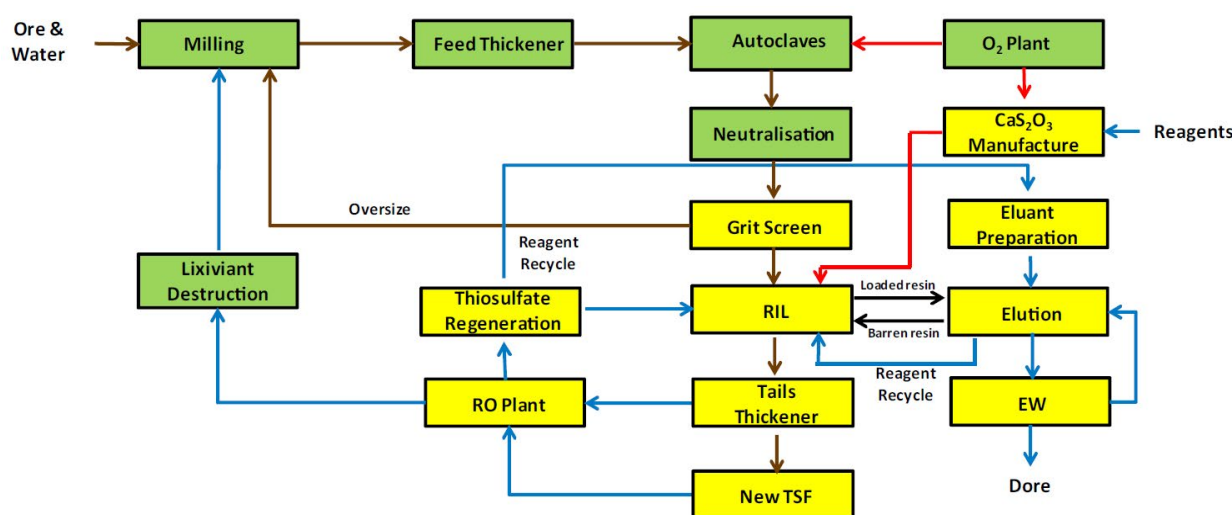


Fig. 3. Barrick Gold Corporation's thiosulfate leaching process flowsheet at Goldstrike (Nevada/USA) (Aylmore, 2016)

3.2. Thiourea

The dissolution of gold by acidic thiourea is much faster than by cyanidation. Compared with cyanide, thiourea has a low sensitivity to base metals (Pb, Cu, Zn, As) and residual sulfur in calcines. It allows high gold recovery from pyrite and chalcopyrite concentrates, and satisfactory recovery of gold from carbonaceous (refractory) ores (Tremblay et al. 1996; Deng et al. 2001; Hilson und Monhemius 2006). Pilot and in situ leaching tests were reported by several researchers. In comparative studies, gold recovery in thiourea leaching was often a similar to cyanide leaching, but thiourea consumption (9 – 10 kg/t) was much higher than cyanide consumption (2.5 - 3 kg/t). (Kavanagh et al.; van Staden und Laxen 1989; Tremblay et al. 1996).

The high consumption of thiourea appears to be the most serious drawback. Other disadvantages include its complexity of leaching reactions, corrosive solution, low selectivity, complicated reagent regeneration, and difficult gold recovery from PLS. The overall operating cost incurred by high thiourea consumption is estimated to be at least twice the cost of cyanide leaching for the same ore. (Aylmore 2016).

3.3. Halides

Halide leaching involves leaching with chloride/chlorine, bromide/bromine and iodide/iodine lixiviant systems (Konyratbekova et al., 2015). The history of halide leaching of gold dates to the early 19th century. Chlorination was a common process used for extraction of gold from ores before cyanide leaching and is currently industrially used worldwide for refining of gold and platinum group metals (PGM).

The Platsol process was successfully demonstrated for the extraction of gold from Cu/Ni/PGM and copper-gold concentrates with gold extraction of >90% for non-preg-robbing refractory gold concentrates. After leaching and S/L separation, gold/PGM can be recovered from pregnant leach solutions by precipitation with NaHS. A feasibility study concluded that the process has "potential to generate positive economic returns" (Dreisinger et al., 2018; Ferron et al., 2003; Zachary J. Black et al. 2018). Kell process involves two-stages: first Cu/Ni/Co sulfides are oxidized in autoclaves (200-225°C, 3000 kPa, 20-45 min.) using sulphate solutions (Adams et al., 2015), second roasting at 900 °C to generate soluble sulphate salts. A 3.5 M HCl solution was used with chlorine at 80 °C for gold extraction. The process was demonstrated at pilot scale and a full-scale plant is considered (Adams et al., 2015; Chadwick, 2017). Similar leach conditions are employed in Intec and N-Chlo processes, which use mixed chloride/bromide solutions with cupric ions (Cu²⁺) as oxidant for pyritic/arsenopyritic gold concentrates (Abe et al., 2008; Moyes et al., 2005). Gold is recovered from PLS by

activated carbon or ion exchange with the latter being more selective. Intec process was tested at pilot scale while a demonstration plant for N-Chlo process was established and operated in Perth (Australia). DST (formerly Nichromet) process is also a mixed chloride/bromide leaching process similar to Intec and N-chlo but differs from these processes by using Cl₂/Br₂ as the oxidant at low temperatures (35 - 45 °C) (Aylmore, 2016). In addition, the process includes roasting as a pre-treatment stage to remove sulfides prior to gold leaching. Hypochlorite (OCl⁻) and hypobromite (OBr⁻) used as a source of Cl₂ and Br₂, respectively, are generated by electrolysis. The process was tested at pilot and demonstration scale (Chadwick, 2017; DST, 2018). Outotec's mixed chloride/bromide based leaching process is performed at 80 - 90 °C under atmospheric conditions in the presence of cupric ions. Gold recovery from PLS is carried out by solvent extraction using an own developed organic reagent (Lundström et al., 2015). The process is tested at pilot scale and still under development (Aylmore, 2016).

Fast leaching kinetics and suitability for treatment of refractory sulfide ores are the most important features of halide leaching processes. However, there is no commercial application of halide leaching for gold extraction, due to important shortcomings: high OPEX, high reagent consumption, not suitable for preg-robbing ores, highly corrosive nature and need for closed systems and high reagent cost, particularly for bromine and iodine. Therefore, to date, there is no commercial application of halides for gold extraction from ores/concentrates.

3.4. Further Reagent Alternatives

Further reagents like bisulfides, thiocyanate, ammonia, organic nitriles, or glycine were extensively tested at laboratory scale, with partially promising results in gold recovery. There are several further gold solvents on the market declared as environmentally sound cyanide alternatives, but their composition is not clearly described, or they contain thiocyanates or other compounds, which may form cyanide complexes during leaching. The major limitations of these reagents are, inter alia, high reagent price, low selectivity, high OPEX, environmental and health concerns or a lower gold recovery at similar conditions compared to cyanide. Because of these drawbacks, no further reagents were tested successfully on a pilot or demonstration scale (Sun et al. 2020; Kholov et al. 2021).

4. Conclusion

Despite decades of research and extensive efforts on industrial application tests, there is still no cost-effective universal replacement for the cyanide process. The search for alternative lixiviant systems is

essentially driven by the environmental impact of using cyanide and the inefficiency of cyanide for certain types of refractory ores (e.g., preg-robbing and copper-rich ores). Thiosulfate, thiourea and chloride can be identified as the most promising alternatives to cyanide. One of the significant challenges for the exploitation of non-cyanide lixiviant systems is the availability or development of suitable downstream processes for the recovery of gold from pregnant leach solutions. Thiosulfate is the only alternative reagent developed into commercial application in the Barrick Goldstrike process. Nonetheless, the increasing need for processing more complex gold ores will force an increasing application of cyanide alternatives in the future. On the other side, for the informal or small-scale gold mining sector, no effective approach was found to regulate the hazardous practices, especially the application of mercury. The approaches of banning mercury or implementing a formal registration system for mining activities were not successful, as mining operations take place in abundant places in the absence of authorities. Consequently, the risk of environmental pollution due to amalgamation or improper use of cyanide will continue.

Recycling gold is very energy-efficient and avoids the environmental damage caused by mining and metallurgical operations. While in industrial recycling, gold is dissolved by aqua regia for further refining under safe conditions, including proper effluent treatment, the same technique is applied by informal recyclers in a very hazardous way. Especially electronic waste becomes more and more important for recycling because it is the fastest growing waste stream. Due to a lack of collection systems or improper disposal of electronic equipment, nowadays only half of the gold is recycled from this waste stream. Also, the gold recovery technique may be optimized in terms of being less hazardous, more selective, and faster than state-of-the-art recycling processes, e.g., by the application of thiosulfate. Published work from different researchers and own research work proved the capability of thiosulfate and thiourea for gold recovery from e-waste and similar waste streams. Besides safer working conditions, these reagents showed a faster dissolution rate and were much more selective than cyanide. Thus, the application of cyanide alternative reagents in gold recycling from different secondary resources constitutes a very promising approach, not just for small scale informal recyclers.

References

- Aylmore, M. G. "Alternative lixiviants to cyanide for leaching gold ores." In *Gold ore processing*, pp. 447-484. Elsevier, 2016.
- Birich, Alexander. *Early Stage Gold Recovery from Printed Circuit Boards via Thiosulfate Leaching*. Shaker Verlag, 2020.
- Birich, Alexander, Zixi Gao, Dzeneta Vrucak, and Bernd Friedrich. "Sensitivity of Gold Lixiviants for Metal Impurities in Leaching of RAM Printed Circuit Boards." *Metals* 13, no. 5 (2023): 969.
- Birich, Alexander, Seifeldin Raslan Mohamed, and Bernd Friedrich. "Screening of non-cyanide leaching reagents for gold recovery from waste electric and electronic equipment." *Journal of Sustainable Metallurgy* 4 (2018): 265-275.
- Birich, Alexander, Srecko Stopic, and Bernd Friedrich. "Kinetic investigation and dissolution behavior of cyanide alternative gold leaching reagents." *Scientific reports* 9, no. 1 (2019): 7191.
- Breuer, P. (2017). *Mobile processing plant to reinvigorate small capital gold mining*. In: *Kalgorlie Metallurgical Symposium (MetFest)*, <https://pdf4pro.com/view/mobile-processing-plant-to-reinvigorate-small-capital-gold-40d01f.html>, Accessed: 20.6.2023.
- Chakraborty, Paromita, Sakthivel Selvaraj, Masafumi Nakamura, Balasubramanian Prithiviraj, Alessandra Cincinelli, and John J. Bang. "PCBs and PCDD/Fs in soil from informal e-waste recycling sites and open dumpsites in India: levels, congener profiles and health risk assessment." *Science of the Total Environment* 621 (2018): 930-938.
- Chi, Xinwen, Martin Streicher-Porte, Mark YL Wang, and Markus A. Reuter. "Informal electronic waste recycling: A sector review with special focus on China." *Waste management* 31, no. 4 (2011): 731-742.
- Choi, Y. "Selecting the best process for the treatment of a refractory gold ore-Barrick's experience." In *ALTA Gold-PM Conference*, pp. 21-18. 2016.
- Choi, Y.; Chefai, S.: Co-current and counter current resin-in-leach in gold leaching processes. Veröffentlichungsnr: US8715389B2.
- Choi, Y., J. Y. Baron, Q. Wang, J. Langhans, and P. Kondos. "Thiosulfate processing— from lab curiosity to commercial application." In *Proceedings of the World Gold*, pp. 45-50. 2013.
- Deng, T. L., M. X. Liao, M. H. Wang, Y-W. Chen, and N. Belzile. "Enhancement of gold extraction from biooxidation residues using an acidic sodium sulphite-thiourea system." *Minerals engineering* 14, no. 2 (2001): 263-268.
- Evans et al.: Goldstrike Mine, Project #2691, Technical Report NI 43-101. In: *BarrickGold - Technial Reports* (2017).
- Fernandez, Jessica, and Christie Klimas. "A Life Cycle Assessment of Jewelry." *DePaul Discoveries* 8, no. 1 (2019): 6.
- Fritz, Benjamin, Carin Aichele, and Mario Schmidt. "Environmental impact of high-value gold scrap recycling." *The international journal of life cycle assessment* 25 (2020): 1930-1941.
- Gökelma, Mertol, Alexander Birich, Srecko Stopic, and Bernd Friedrich. "A review on alternative gold recovery re-agents to cyanide." *Journal of Materials Science and Chemical Engineering* 4, no. 08 (2016): 8.
- Heselev, T. (2017): *Unlocking Australia Ores - Golden Alternative*. In: *CSIRO Journal*.
- Hilson, Gavin, and A. J. Monhemius. "Alternatives to cyanide in the gold mining industry: what prospects for the future?." *Journal of Cleaner production* 14, no. 12-13 (2006): 1158-1167.
- Kahhat, Ramzy, Eduardo Parodi, Gustavo Larrea-Gallegos, Carlos Mesta, and Ian Vázquez-Rowe. "Environmental impacts of the life cycle of alluvial gold mining in the Peruvian Amazon rainforest." *Science of the Total Environment* 662 (2019): 940-951.
- P. F. Kavanagh, B. F. Foley, J. McLoughlin, P. Owens, S. A. Curran, C. McNamee, and K. Mullins. "Leaching and recovery of gold by use of acido-thiourea on copper-mine wastes: laboratory and pilot-plant tests and process modelling. In *Hydrometallurgy'94: Papers presented at the international symposium 'Hydrometallurgy'94 organized by the Institution of Mining and Metallurgy and the Society of Chemical Industry, and held in Cambridge, England, from 11 to 15 July, 1994*, pp. 441-461. Springer Netherlands, 1994.
- Kholov, K.I., Nasim T. Sharifboev, Shonavrur R. Samikhov, Sherzod R. Dzhurakulov, and Mahjuba S. Zarifova. "Gold Leaching by Various Solutions, Alternative of Cyanide and Their Prospects in the Future." *Journal of Siberian Federal University. Engineering & Technologies* 14, no. 4 (2021): 433-447.
- Kolen, Judith, M. E. M. de Theije, and Armin Mathis. "Formalized small-scale gold mining in the Brazilian Amazon: an activity surrounded by informality." In *Small-scale Gold Mining in the Amazon. The cases of Bolivia, Brazil, Colombia, Peru and Suriname*, pp. 31-45. CEDLA, 2013.
- Kolen, Judith, Eline de Smet, and Marjo de Theije. "We are all Garimpeiros: Settlement and Movement in Communities of the Tapajós Small-Scale Gold Mining Reserve." *The Journal of Latin American and Caribbean Anthropology* 23, no. 1 (2018): 169-188.
- Latacz, Damien, Fabian Diaz, Alexander Birich, Benedikt Flerus, and Bernd Friedrich. "WEEE Recycling at IME-RWTH Aachen: From Basic Metal Recovery to Resource Efficiency." *World Metall.-ERZMETALL* 73 (2020): 155-162.
- Marsden, John, and Iain House. *The chemistry of gold extraction*. SME, 2006.
- Molleman, Ellen, and David Dreisinger. "The treatment of copper-gold ores by ammonium thiosulfate leaching." *Hydrometallurgy* 66, no. 1-3 (2002): 1-21.
- Paddock, R. C. "The Hidden Cost of Gold: Birth Defects and Brain Damage." *New York Times*. <https://www.nytimes.com/2019/11/09/world/asia/indonesia-mercury-pollution-gold-mining.html> (2019).
- Satriastanti, F. E. (2015): *Indonesia's mercury policy a good start, but kinks remain*. F. E. Satriastanti. Hg. v. Mongbabay. Mongbabay. Online: <https://news.mongabay.com/2015/09/indonesias-mercury-policy-a-good-start-but-kinks-remain/>, Accessed at 20.04.2023.
- Springer, Sally K., Bernhard G. Peregovich, and Mario Schmidt. "Capability of social life cycle assessment for analyzing the artisanal small-scale gold mining sector—case study in the Amazonian rainforest in Brazil." *The International Journal of Life Cycle Assessment* 25 (2020): 2274-2289.
- Sun, Chun-bao, Xiao-liang Zhang, Jue Kou, and Yi Xing. "A review of gold extraction using noncyanide lixivants: Fundamentals, advancements, and challenges toward alkaline sulfur-containing leaching agents." *International Journal of Minerals, Metallurgy and Materials* 27 (2020): 417-431.
- Tremblay, L., G. Deschenes, E. Ghali, J. McMullen, and M. Lanouette. "Gold recovery from a sulphide bearing gold ore by percolation leaching with thiourea." *International Journal of Mineral Processing* 48, no. 3-4 (1996): 225-244.
- Van Staden, PJ & Laxen, P. A. "In-stope leaching with thiourea." *Journal of the Southern African Institute of Mining and Metallurgy* 89, no. 8 (1989): 221-229.
- Wan, Rong-Yu, and K. Marc LeVier. "Solution chemistry factors for gold thiosulfate heap leaching." *International Journal of Mineral Processing* 72, no. 1-4 (2003): 311-322.
- West-Sells, P. G., and R. P. Hackl. "A novel thiosulfate leach process for the treatment of carbonaceous gold ores." *Treatment of Gold Ores. The Canadian Institute of Mining, Metallurgy and Petroleum, Montreal, Canada* 209 (2005): 223.
- Wotruba, Hermann, Thomas Hentschel, Karen Livan, Felix Hruschka, and Michael Priester. "Environmental management in small-scale mining." CID-Plural publishers, the Peace, Bolivia (1998).
- Xia, Chen. *Associated sulfide minerals in thiosulfate leaching of gold: problems and solutions*. Queen's University, 2008.
- Feng, X. I. E., Jun-nan CHEN, W. A. N. G. Jian, and W. A. N. G. Wei. "Review of gold leaching in thiosulfate-based solutions." *Transactions of Nonferrous Metals Society of China* 31, no. 11 (2021): 3506-3529.
- Zachary J. Black et al.: *Technical Report NORTHMET PROJECT. Form NI 43-101F1 Technical Report*, (2018) https://polymetmining.com/wp-content/uploads/2018/10/PN150163-PolyMet-NI-43-101-Technical-Report-2018_03_26_Rev0.pdf, Accessed 20.6.2023.
- Zhang, Hongguang, and David B. Dreisinger. "The recovery of gold from ammoniacal thiosulfate solutions containing copper using ion exchange resin columns." *Hydrometallurgy* 72, no. 3-4 (2004): 225-234.